



UvA-DARE (Digital Academic Repository)

Concentration dependence of the pseudometamagnetic transition field in heavy-fermion $Ce_{1-x}Y_xRu_2Si_2$

Haen, P.; de Visser, A.; Lapierre, F.

Publication date

1995

Published in

Physica B-Condensed Matter

[Link to publication](#)

Citation for published version (APA):

Haen, P., de Visser, A., & Lapierre, F. (1995). Concentration dependence of the pseudometamagnetic transition field in heavy-fermion $Ce_{1-x}Y_xRu_2Si_2$. *Physica B-Condensed Matter*, 140-144, 230-232.

General rights

It is not permitted to download or to forward/distribute the text or part of it without the consent of the author(s) and/or copyright holder(s), other than for strictly personal, individual use, unless the work is under an open content license (like Creative Commons).

Disclaimer/Complaints regulations

If you believe that digital publication of certain material infringes any of your rights or (privacy) interests, please let the Library know, stating your reasons. In case of a legitimate complaint, the Library will make the material inaccessible and/or remove it from the website. Please Ask the Library: <https://uba.uva.nl/en/contact>, or a letter to: Library of the University of Amsterdam, Secretariat, Singel 425, 1012 WP Amsterdam, The Netherlands. You will be contacted as soon as possible.



ELSEVIER

Physica B 211 (1995) 230–232

PHYSICA B

Concentration dependence of the pseudometamagnetic field in heavy fermion $Ce_{1-x}Y_xRu_2Si_2$

P. Haen^{a,*}, A. de Visser^b, F. Lapierre^a^aCRTBT[†], CNRS, BP 166, 38042 Grenoble cedex 9, France^bVan der Waals–Zeeman Laboratory, Valckenierstraat 65, 1018 XE Amsterdam, The Netherlands

Abstract

Magnetization measurements performed on $Ce_{1-x}Y_xRu_2Si_2$ single crystals at low temperature for the magnetic field parallel to the easy magnetization axis (*c*-axis of the tetragonal structure) are reported. They show an increase of the metamagnetic-like field H_M , from about 8 T for $x = 0$ to a value of 20 T for $x = 0.1$. The Grüneisen parameter derived from this increase of H_M is compared to those already derived from other experiments, especially from the variation of T_K deduced from specific heat measurements.

The heavy fermion compound $CeRu_2Si_2$ is known to exhibit a metamagnetic-like transition for a field of $H_M \approx 8$ T applied along the tetragonal *c*-axis [1–3]. This transition is associated with the disappearance of short range antiferromagnetic (AF) correlations which have been observed by neutron scattering experiments [4]. Nevertheless, and although recent muon experiments suggest the appearance of tiny magnetic ordered moments ($10^{-3} \mu_B$) below $T_N \approx 1.5$ K [5], the ground state of $CeRu_2Si_2$ can be considered as a Pauli paramagnet [4,6]. This certainly results from a strong competition with the Kondo effect. A Kondo temperature of $T_K = 24$ K has been deduced from specific heat [1] as well as from neutron scattering [4] data.

Application of pressure drives $CeRu_2Si_2$ toward a less magnetic state, leading, especially, to an increase of H_M , a reduction of the coefficient *A* of the low temperature resistivity AT^2 variation and an increase of the temperature of the susceptibility maximum [6]. All these effects are witnessed by a large value of the Grüneisen parameter, $\Gamma \approx 180$, either magnetic (from the variation of

H_M) or thermal (variation of a characteristic temperature derived from other parameters). This nice scaling is limited to a small pressure range ($\lesssim 6$ kbar) [6,7]. For higher pressures, $CeRu_2Si_2$ enters into an intermediate valence (IV) state.

A similar volume reduction, equivalent to a positive pressure effect, can be induced by substitution of Ce by Y, while substitution of Ce by La is in first approximation equivalent to a negative pressure effect. Although these alloying processes modify the number of Ce atoms and induce disorder in the lattice, a concomitant increase or reduction, respectively, of the value of T_K was derived [1,8] from the low temperature specific heat of $Ce_{1-x}Y_xRu_2Si_2$ and $Ce_{1-x}La_xRu_2Si_2$ alloys. These variations of T_K also lead to a Grüneisen parameter $\Gamma = -\partial \ln T_K / \partial \ln V$ of the order of 180, for a concentration range of substituted non-magnetic atoms going from 30% of La to 10% of Y. From the earlier reported [9] variation of the 4.2 K values of H_M versus concentration (from $x = 0.13$ of La up to $x = 0.05$ of Y), it is not clear whether H_M also scales with T_K in these alloys. For 5% of Y, $H_M = 13.2$ T. It seemed interesting to measure the magnetization of samples of higher Y concentrations, in order first to check the scaling law, and second to check

* Corresponding author.

[†] Laboratoire associé à l'Université Joseph Fourier, Grenoble.

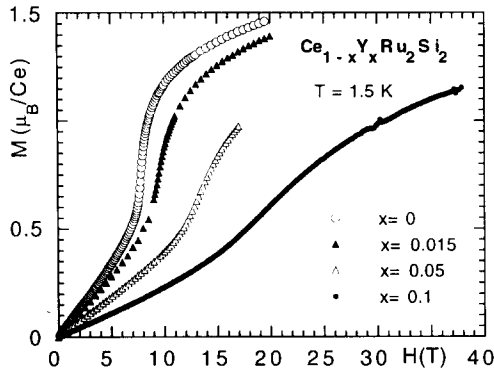


Fig. 1. Variation of the magnetization M versus H of $Ce_{1-x}Y_xRu_2Si_2$; (○): $x = 0$; (▲): $x = 0.015$; (△): $x = 0.05$; (●): $x = 0.10$.

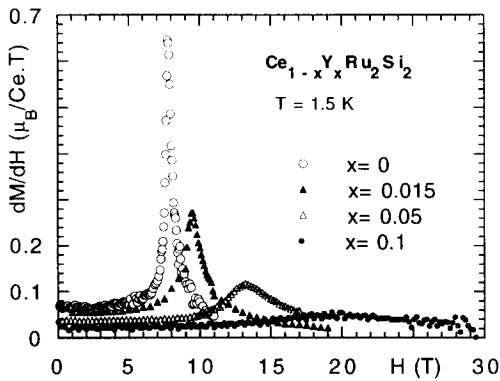


Fig. 2. Variation of the derivative of the magnetization, $\partial M/\partial H$ versus H of $Ce_{1-x}Y_xRu_2Si_2$; symbols have the same meaning as in Fig. 1.

whether the metamagnetic-like transition will disappear when the system is driven into an IV state.

Here we report on magnetization measurements performed on a series of $Ce_{1-x}Y_xRu_2Si_2$ single crystals with concentrations $x = 0, 0.015, 0.05$ and 0.1 , with the field applied along the c -axis. The first two crystals are those previously used for magnetostriction experiments [10, 11]. They were measured up to 20 T at the High Field Magnet Laboratory in Grenoble by a standard extraction technique. The third is the same as in Ref. [9]. The $x = 0.10$ crystal has been measured up to 40 T in the pulse magnet at the University of Amsterdam.

The magnetization curves at 1.5 K are plotted in Fig. 1 and their derivatives are shown (only up to 30 T) in Fig. 2. The values of several parameters characterising these curves are reported in Table 1. The values of H_M are known to vary slightly with temperature [2, 3, 10, 11], but those reported here for $x = 0$ and $x = 0.015$ are close to

Table 1

Characteristics of the magnetization of $Ce_{1-x}Y_xRu_2Si_2$ alloys for a magnetic field along the easy direction

x	H_M (T)	$M(H_M)$ (μ_B/Ce)	$dM/dH(H_M)$ ($\mu_B/Ce T$)
0	7.74	0.72	0.646
0.015	9.45	0.75	0.273
0.05	13.2	0.65	0.178
0.1	19.3	0.575	0.0557

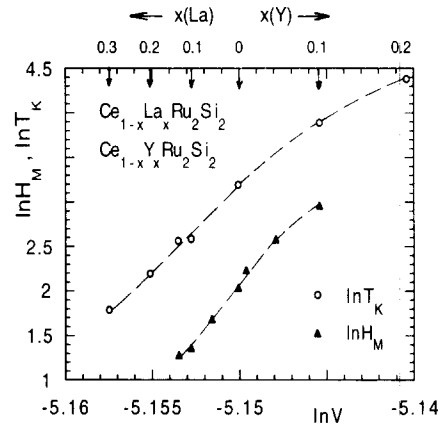


Fig. 3. Plot of $\ln H_M$ and $\ln T_K$ versus $\ln V$ for $Ce_{1-x}La_xRu_2Si_2$ and $Ce_{1-x}Y_xRu_2Si_2$. The concentrations are indicated on the top of the figure. The $\ln T_K$ values are taken from Ref. [8].

the $T \rightarrow 0$ values already reported [10, 11]. Fig. 2 shows the dramatic reduction of the values of dM/dH at $H = H_M$ and the broadening of the peak on alloying also mentioned previously. These effects would be even stronger if we could compare dM/dH values at lower temperatures, since the peak is known to increase further and to become narrower on cooling, especially for the pure compound, while $(dM/dH)^{-1}$ saturates rapidly below 1 K in alloys [12]. Another interesting feature, seen from Table 1 is that the value of M at H_M is almost independent of x for small x ; the same value $M(H_M) = 0.75 \mu_B/Ce$ is found for $x = 0.015$ of Y and for $x = 0.05$ of La, which is even slightly higher than for $x = 0$. This is a good confirmation of the scaling properties already reported [6].

The values of H_M vary quite linearly with yttrium concentration. In order to derive the corresponding Grüneisen parameter we have plotted in Fig. 3 the variations of $\ln H_M$ versus $\ln V$. We have added data points corresponding to H_M for $x = 0.05, 0.1$ and 0.13 of La ($= 5.67, 5.9$ and 5.6 T, respectively). (For La concentrations $x \geq 0.08$, the alloys order at low temperature, but

H_M disappears only for $x \geq 0.2$. However, it is not easy to determine its value below T_N [3].) The values of V were interpolated from those given in Ref. [8]. The concentrations are indicated on the top of the figure. For comparison, we have also reported in Fig. 3 the variations of $\ln T_K$ versus $\ln V$ taken from this reference. Lines are drawn through the points as guides for the eyes. In both cases, the $x = 0.1$ (Y) data point deviates from a mean straight line; this effect becomes stronger for $x = 0.2$ (Y), as far as T_K is concerned. Clearly, the slope of the line around $x = 0$ is larger for H_M than for T_K . From T_K , Γ lies between 175 and 195, within the experimental scattering, while from H_M , one can derive a value of Γ ranging from about 235 to 270. (The fact that the H_M values are not taken exactly for $T = 0$, induces a negligible error compared to the apparent scattering of the data.)

Surprisingly, the above Γ value is the highest ever found for CeRu_2Si_2 . However, this cannot be taken as an argument against the assumption [6, 10] that the thermal and magnetic Grüneisen parameters are identical in the system. Moreover, it has been noticed that alloying effects increase Γ instead of decreasing it: a value of ≈ 200 has been found for 5% of La against ≈ 180 for CeRu_2Si_2 [10]. The latter values were deduced assuming a compressibility, κ , of the order of 1. Taking $\kappa = 0.82$, as measured [7], one gets $\Gamma \approx 200$ for CeRu_2Si_2 and ≈ 240 for the 5% La alloy, which become closer to the value derived from the present study.

Finally, by extrapolating the H_M data of Fig. 3 similarly to the T_K points, one could expect a H_M value of the order of 30 T for an alloy with 20% of Y. However, according to the results in Figs. 1 and 2, the magnetization of such an alloy would show only a tiny inflexion point or perhaps no anomaly anymore.

We wish to thank Dr. P. Lejay who prepared the single crystals, Dr. J. Voiron for his help in some of the magnetization measurements, and Drs. M.J. Besnus and A. Meyer for allowing us to reproduce T_K values from Ref. [8].

References

- [1] M.J. Besnus, J.P. Kappler, P. Lehmann and A. Meyer, *Solid State Commun.* 55 (1985) 779.
- [2] P. Haen, J. Flouquet, F. Lapierre, P. Lejay and G. Remenyi, *J. Low Temp. Phys.* 67 (1987) 391.
- [3] R.A. Fisher, C. Marcenat, N.E. Phillips, P. Haen, F. Lapierre, P. Lejay, J. Flouquet and J. Voiron, *J. Low Temp. Phys.* 84 (1991) 49.
- [4] J. Rossat-Mignod, L.P. Regnault, J.L. Jacoud, C. Vettier, P. Lejay, J. Flouquet, E. Walker, D. Jaccard and A. Amato, *J. Magn. Magn. Mater.* 76&77 (1988) 376.
- [5] A. Amato, C. Baines, R. Feyerherm, J. Flouquet, F.N. Gygax, P. Lejay, A. Schenck and U. Zimmermann, *Physica B* 186–188 (1993) 276.
- [6] J.M. Mignot, J. Flouquet, P. Haen, F. Lapierre, L. Puech and J. Voiron, *J. Magn. Magn. Mater.* 76&77 (1988) 97.
- [7] K. Payer, P. Haen, J.M. Laurant, J.M. Mignot and J. Flouquet, *Physica B* 186–188 (1993) 503.
- [8] M.J. Besnus, P. Lehmann and A. Meyer, *J. Magn. Magn. Mater.* 63&64 (1987) 323; P. Lehmann, Ph.D. Thesis, Strasbourg (1987), unpublished.
- [9] P. Haen, J.P. Kappler, F. Lapierre, P. Lehmann, P. Lejay, J. Flouquet and A. Meyer, *J. Physique (Paris) Colloq.* 49 (1988) C8–757.
- [10] C. Paulsen, A. Lacerda, L. Puech, P. Haen, J.L. Tholence, P. Lejay, J. Flouquet and A. de Visser, *J. Low Temp. Phys.* 81 (1990) 317.
- [11] S. Holtmeier, P. Haen, A. de Visser, A. Lacerda, P. Lejay and J. Flouquet, *Physica B* 186–188 (1993) 521.
- [12] S. Holtmeier, P. Haen, A. Lacerda, P. Lejay, J.L. Tholence, J. Flouquet and J. Voiron, *Physica B* 204 (1995) 250.